

Elite Textile Trading LLC

Quote for Vinyl Sheeting

Contact: Huasong Yin

Tel: 1-949-899-0101

Fax: 1-949-317-0555

Email: michael@elitetex.us/elite@elitetex.us

Add: 30021 Tomas street, suite 110, Rancho Santa Margarita, CA, 92688

FEIN: 47-1477170

CAGE CODE: 7B4D4

DUNS: 079645258

SAM STATUS: ACTIVE

Origin: China


Delivery: 40-70 days ARO.

Quote date: 03/22/2023

Print Signature: Huasong Yin

Title: President

Signature:

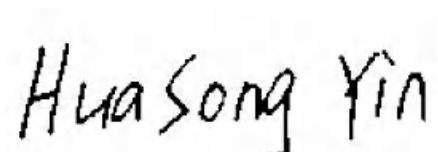A handwritten signature in black ink that reads "Hua Song Yin". The signature is written in a cursive, slightly slanted style. The first name "Hua" is written with a large, looped 'H'. The last name "Yin" is written with a large, looped 'Y'.

Literature

Item: Vinyl Sheeting

Description:

Item No: U type-01


Color: Grey

Material: Vinyl


Dimensions: 20' Length or Customized, 24" Width(606mm), 9"

Depth(230mm), 0.354" Thickness(9mm)

Unit Price: \$243.6 each

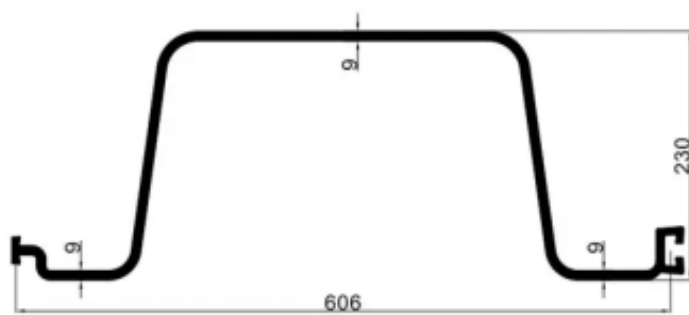

Vinyl sheet pile

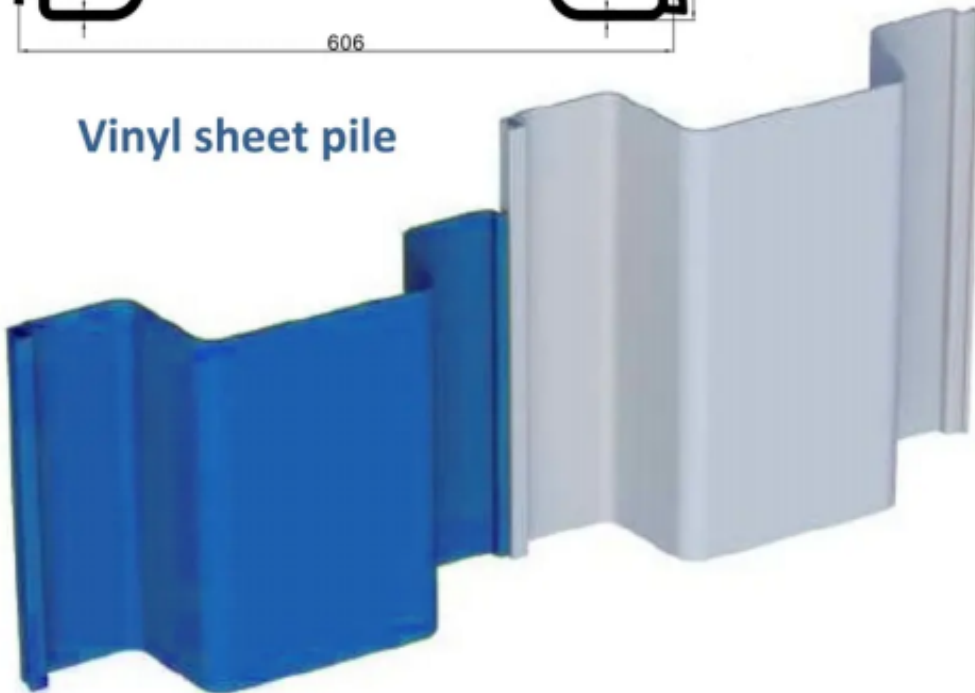

Item No: U718


Color: Grey

Material: Vinyl

Dimensions: 20' Length or Customized, 28.3" Width(718mm), 7"

Depth(180mm), 0.393" Thickness(10mm)

Unit Price: \$289.2 each

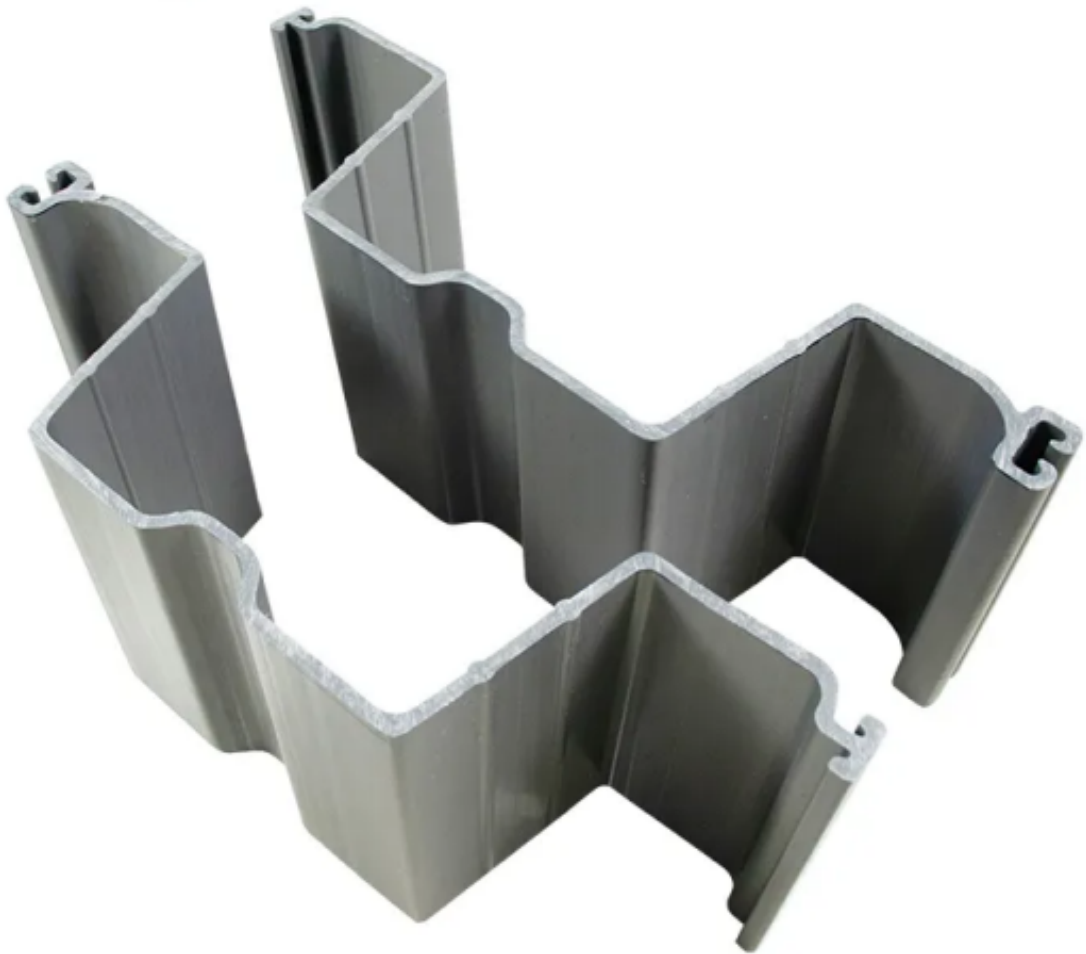

TEST REPORT

No. : SHMR221101352201

Date : Dec 07, 2022

Page: 2 of 7

Summary of Results:

No.	Test Item	Test Method	Result	Conclusion
1	Density	GB/T 1033.1-2008	1.440 g/cm ³	/
2	Shore Hardness	GB/T 2411-2008	D/15:78	/
3	Tensile Strength	GB/T 1040.1-2018 & GB/T 1040.2-2006	45.4 MPa	/
	Elongation at Break		98 %	/
	Elasticity Modulus		3070 MPa	/
4	Flexural Strength	GB/T 9341-2008	75.8 MPa	/
	Flexural Modulus		2890 MPa	
5	Deflection Temperature under Load	GB/T 1634.1-2019 & GB/T 1634.2-2019 Method A	74.3 °C	/

Note: Pass : Meet the requirements;
Fail : Does not meet the requirements;
/ : Not Apply to the judgment.

TEST REPORT

序号 Serial No.	检测项目 Test Items	技术要求 Requirement	检测结果 Test Results	单项结论 Item Conclusion	备注 Remarks
1	拉伸强度 Tensile strength MPa	/	45.0	/	/
2	维卡软化温度 Vicat softening temperature ℃	/	82.4	/	/
3	弯曲强度 Bending strength MPa	/	75.8	/	/
4	密 度 Density g/cm ³	/	1.425	/	/
5	弯曲弹性模量 Flexural modulus of elasticity MPa	/	2538	/	/
6	长 度 Length mm	/	999	/	/
7	宽 度 Width mm	/	705	/	/
8	简支梁缺口冲击强度 Simply supported beam notched impact strength kJ/m ²	/	7.1	/	/
9	悬臂梁冲击强度 Lzod impact strength kJ/m ²	/	11	/	/
10	负荷变形温度 (弯曲应力: 1.80MPa) ℃ Load deformation temperature (Bending stress: 1.80MPa)	/	66.4	/	/
11	硬度 (邵尔 D) Hardness (Shore D)度	/	79	/	/
12	压缩强度 Compressive strength	/	67.2	/	/

（报告专用章）