

January 5, 2021

▪TEST REPORT▪

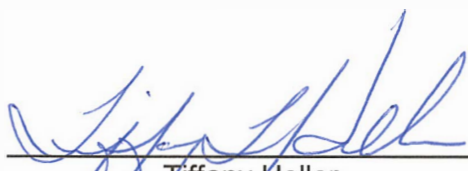
PN 156551

PHARMACEUTICAL SERVICES


Prepared For:

John Zhao
Intco Medical Industries Inc.
805 Barrington Avenue
Ontario, CA 91764

Prepared By:


Tiffany Heller
Manager, Pharmaceutical Services

Approved By:


Ana C Barbur, M.S.
Vice President, Analytical & Chemical Services

Rev 101218



An A2LA ISO 17025 Accredited Testing Laboratory — Certificate Numbers 255.01 & 255.02
ISO 9001:2015 Registered

ISO 9001:2015
Registered

Letters and reports are for the exclusive use of the clients to whom they are addressed and shall not be reproduced, except in full, without the written permission of Akron Rubber Development Laboratory, Inc. (ARDL). The information contained herein applies to the specific material, products or processes tested or evaluated. No warranty of any kind is herein construed or implied. The liability of ARDL, Inc. shall be limited to the amount of consideration paid for services. ARDL, Inc. is ISO 17025 accredited by A2LA for the test methods listed on the referenced certificates.

January 5, 2021

John Zhao
Intco Medical Industries Inc.

Page 2 of 5
PN 156551

SUBJECT: Permeation testing per ASTM D6978 on sample submitted by the above company.

RECEIVED: One (1) glove type identified as; Synmax Vinyl Exam Glove.

TEST CHEMICALS:

Table 1. List of the Testing Drugs and their Sources

TESTING CHEMOTHERAPY DRUGS	DRUG SOURCE
Carmustine (BCNU), 3.3 mg/ml (3,300 ppm)	Sigma Aldrich; Batch# 0000095754; Expiration 10/2021
Cisplatin, 1.0 mg/ml (1,000 ppm)	Accord; Lot# P2001296; Expiration 01/2022
Cyclophosphamide (Cytosan), 20.0 mg/ml (20,000 ppm)	Accord; Lot# 19112225; Expiration 10/2021
Dacarbazine, 10.0 mg/ml (10,000 ppm)	Teva; Lot# 31325414B; Expiration 09/2021
Doxorubicin HCl, 2.0 mg/ml (2,000 ppm)	WestWard; Lot# BJ0051; Expiration 06/2021
Etoposide, 20.0 mg/ml (20,000 ppm)	Teva; Lot# 31325485B; Expiration 07/2021
Fluorouracil, 50.0 mg/ml (50,000 ppm)	Accord; Lot# P2001167; Expiration 01/2022
Paclitaxel, 6.0 mg/ml (6,000 ppm)	Teva; Lot# 19K24KA; Expiration 11/2021
ThioTepa, 10.0 mg/ml (10,000 ppm)	USP; Lot # R11380; Expiration 09/2021

COLLECTION MEDIA:

Table 2. Collection Media for Test Drug

TEST DRUG AND CONCENTRATION	COLLECTION MEDIUM
Carmustine (BCNU), 3.3 mg/ml (3,300 ppm)	10% Ethanol Aqueous Solution
Cisplatin, 1.0 mg/ml (1,000 ppm)	Distilled Water
Cyclophosphamide (Cytosan), 20.0 mg/ml (20,000 ppm)	Distilled Water
Dacarbazine, 10.0 mg/ml (10,000 ppm)	Distilled Water
Doxorubicin HCl, 2.0 mg/ml (2,000 ppm)	Distilled Water
Etoposide, 20.0 mg/ml (20,000 ppm)	Distilled Water
Fluorouracil, 50.0 mg/ml (50,000 ppm)	9.20 pH Sodium Hydroxide Solution
Paclitaxel, 6.0 mg/ml (6,000 ppm)	30% Methanol Aqueous Solution
ThioTepa, 10.0 mg/ml (10,000 ppm)	Distilled Water

*ARDL is ISO 17025 accredited by A2LA for the test methods listed on the certificates referenced on page one. Unless specified, the current specification version is used.

NOTE: Non-ISO 17025 accredited test methods are designated with the ^ symbol to differentiate from ISO 17025 accredited methods in the body of the test report. *

www.ardl.com | 2887 Gilchrist Rd. | Akron, Ohio 44305 | answers@ardl.com | Toll Free (800) 830-ARDL

Fax (330) 794-6610 | Worldwide (330) 794-6600

TESTING CONDITIONS:

Standard Test Method Used:	ASTM D6978
Analytical Method:	UV/VIS Spectrometry
Testing Temperature:	35.0°C ± 2.0
Collection System:	Closed Loop
Specimen Area Exposed:	5.067 cm ²
Selected Data Points:	25/test
Number of Specimens Tested:	3/test
Location Sampled From:	Cuff

DETECTION METHOD OF CHEMICAL PERMEATION:**UV/VIS ABSORPTION SPECTROMETRY:**

Instrument: Perkin Elmer UV/VIS Spectrometer Lambda 25

UV/VIS Absorption Spectrometry was used to measure the absorbance of test chemicals, which permeated through the specimens into the collection medium. The collection medium was circulated in a closed loop through the testing period. Data collection was performed according to the programmed schedule by means of UV Winlab software from the Perkin Elmer Corporation. The list of the characteristic wavelengths is shown below.

Table 3. Characteristic Wavelengths used in UV/VIS Absorption Spectrometry

TESTING DRUG	WAVELENGTH (nm)
Carmustine (BCNU), 3.3 mg/ml (3,300 ppm)	229
Cisplatin, 1.0 mg/ml (1,000 ppm)	199
Cyclophosphamide (Cytosan), 20.0 mg/ml (20,000 ppm)	200
Dacarbazine, 10.0 mg/ml (10,000 ppm)	320
Doxorubicin HCl, 2.0 mg/ml (2,000 ppm)	232
Etoposide, 20.0 mg/ml (20,000 ppm)	205
Fluorouracil, 50.0 mg/ml (50,000 ppm)	269
Paclitaxel, 6.0 mg/ml (6,000 ppm)	232
ThioTepa, 10.0 mg/ml (10,000 ppm)	199

SAMPLE CHARACTERISTICS:

Table 4. Thickness characteristics for the tested: One (1) glove type identified as: Synmax Vinyl Exam Glove.

Testing Drug	Thickness (mm)			Average (mm)
	Sample 1	Sample 2	Sample 3	
Carmustine (BCNU)	0.056	0.050	0.050	0.052
Cisplatin	0.055	0.057	0.054	0.056
Cyclophosphamide (Cytosan)	0.056	0.057	0.054	0.056
Dacarbazine	0.051	0.051	0.053	0.052
Doxorubicin	0.051	0.052	0.054	0.052
Etoposide	0.049	0.054	0.051	0.051
Fluorouracil	0.053	0.051	0.055	0.053
Paclitaxel	0.052	0.050	0.054	0.052
ThioTepa	0.057	0.053	0.057	0.056
Weight/Unit Area (g/m²)	62.2			

RESULTS:

Table 5. Permeation Test Results on testing of: One (1) glove type identified as: Synmax Vinyl Exam Glove.

TEST CHEMOTHERAPY DRUGS	AVERAGE BREAKTHROUGH DETECTION TIME (Specimen1/2/3) (Minutes)	AVERAGE STEADY STATE PERM. RATE (Specimen1/2/3) ($\mu\text{g}/\text{cm}^2/\text{minute}$)	OTHER OBSERVATIONS
Carmustine (BCNU), 3.3 mg/ml (3,300 ppm)	12.6 (12.6,13.3,12.7)	0.2 (0.2,0.2,0.1)	Slight swelling and no degradation
Cisplatin, 1.0 mg/ml (1,000 ppm)	>240 min.	N/A	Slight swelling and no degradation
Cyclophosphamide (Cytosan), 20.0 mg/ml (20,000 ppm)	>240 min.	N/A	Slight swelling and no degradation
Dacarbazine, 10.0 mg/ml (10,000 ppm)	>240 min.	N/A	Slight swelling and no degradation
Doxorubicin HCl, 2.0 mg/ml (2,000 ppm)	>240 min.	N/A	Slight swelling and no degradation
Etoposide, 20.0 mg/ml (20,000 ppm)	>240 min.	N/A	Slight swelling and no degradation
Fluorouracil, 50.0 mg/ml (50,000 ppm)	>240 min.	N/A	Slight swelling and no degradation
Paclitaxel, 6.0 mg/ml (6,000 ppm)	>240 min.	N/A	Slight swelling and no degradation
ThioTepa, 10.0 mg/ml (10,000 ppm)	15.4 (15.4,16.3,17.6)	0.6 (0.7,0.6,0.6)	Slight swelling and no degradation

January 5, 2021

John Zhao
Intco Medical Industries Inc.

Page 5 of 5
PN 156551

SAMPLES RECEIVED:

One (1) glove type (2 boxes) identified as: Synmax Vinyl Exam Gloves 100 pieces Size M, 100 Pieces Size Lg



Prepared By: 
Tiffany Heller
Manager, Pharmaceutical Services

Approved By: 
Ana C Barbur, M.S.
Vice President, Analytical & Chemical Services